

LA-UR-01-2939

Approved for public release;
distribution is unlimited.

Title: **PALLADIUM ALLOY COMPOSITE MEMBRANES FOR
HYDROGEN SEPARATION**

Author(s): S. N. Paglieri and S. A. Birdsell

Submitted to:

<http://lib-www.lanl.gov/la-pubs/00796304.pdf>

Los Alamos National Laboratory, an affirmative action/equal opportunity employer, is operated by the University of California for the U.S. Department of Energy under contract W-7405-ENG-36. By acceptance of this article, the publisher recognizes that the U.S. Government retains a nonexclusive, royalty-free license to publish or reproduce the published form of this contribution, or to allow others to do so, for U.S. Government purposes. Los Alamos National Laboratory requests that the publisher identify this article as work performed under the auspices of the U.S. Department of Energy. Los Alamos National Laboratory strongly supports academic freedom and a researcher's right to publish; as an institution, however, the Laboratory does not endorse the viewpoint of a publication or guarantee its technical correctness.

PALLADIUM ALLOY COMPOSITE MEMBRANES FOR HYDROGEN SEPARATION

S. N. Paglieri and S. A. Birdsell

Engineering Sciences & Applications Division
Los Alamos National Laboratory
P.O. Box 1663
Los Alamos, NM 87544

ABSTRACT

High temperature hydrogen separating membranes have the potential to increase the efficiency of the coal-based electrical/chemical plants of the future. Palladium (Pd) alloys are attractive materials as membranes due to high permeability and relative robustness. A main drawback is the high cost of Pd metal so that thin metal films supported by hydrogen porous substrates are imperative. Pure Pd also suffers from hydrogen embrittlement and poor resistance to thermal cycling. Membrane configurations consisting of thin films ($< 20 \mu\text{m}$) of Pd alloys on hydrogen-porous substrates will help to alleviate cost and embrittlement problems. The membranes will be employed in the water gas shift reaction to produce purified hydrogen.

INTRODUCTION

The palladium membrane reactor (PMR) is a combined permeator and catalytic reactor (Figure 1). Catalysts are used to foster reactions such as methane steam reforming, $\text{CH}_4 + \text{H}_2\text{O} \rightarrow 3\text{H}_2 + \text{CO}$, and water-gas shifting, $\text{H}_2\text{O} + \text{CO} \rightarrow \text{H}_2 + \text{CO}_2$. Due to thermodynamic equilibrium limitations these reactions only proceed to partial completion. Thus, a tubular PdAg_{23} (wt.%) membrane with $\sim 175 \mu\text{m}$ thick walls, which is exclusively permeable to H_2 , was incorporated into the reactor. By maintaining a H_2 -partial-pressure gradient across the membrane, H_2 removal through the membrane enabled the reactions to proceed toward the product side.

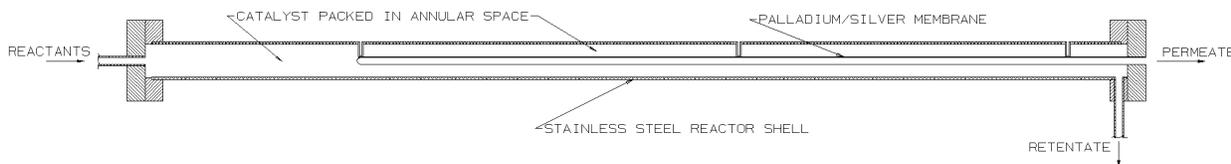


Figure 1. The Palladium Membrane Reactor.

PMR's have significant advantages in efficiency over other fuel processing systems. Several components are usually required in conventional steam reforming systems. For example, a high-temperature reformer, a low-temperature reformer, a high-temperature shifter, and a low-temperature shifter are typically used in methane steam reforming to obtain as much pure H_2 as possible. Heat exchange, gas separation, and air or water injection are required between reactors, resulting in expensive control systems, multiple unit operations, and high energy consumption. In addition, a large quantity of excess water and high operating temperatures ($\sim 800^\circ\text{C}$ in the case of methane) are needed to obtain good conversion and prevent coking (carbon deposition on the catalyst). The multiple process steps, excess water requirements, and high operating temperatures of a conventional reformer result in a large and inefficient system. With a PMR

system only one reactor is required and it operates at a lower, more efficient temperature than conventional reformers and requires a lower steam/hydrocarbon ratio.

PMR's have been used to convert hydrocarbons into pure H₂¹⁻⁷. This process holds promise for generating H₂ for fuel cell use or for H₂-consuming reactions in the chemical and petrochemical industries. The PMR has been under development at Los Alamos since 1992 (refs. 1-7). During this time, PMR performance has been characterized with respect to inlet conditions (i.e., hydrocarbon-to-water ratio), temperature, pressure, geometry, and catalyst type. This information has been analyzed and incorporated into a mechanistic model for use in design and optimization. The PMR system has run for 215 days of around-the-clock operation over an 18-month period with high performance and reliability. Thus far, simulated coal gas, methane, methanol, ethanol, octane, and gasoline have been reformed in a PMR. Upwards of 99% of all the injected H₂ (in the form of water and hydrocarbons) were converted to pure H₂ for each of the fuels. The retentate (i.e., effluent from the high-pressure side of the reactor) was essentially pure CO₂ for each of the fuels, with the impurities consisting of a small quantity of unreacted fuel, H₂, H₂O, CH₄, and CO.

Although membrane reactors hold the promise of improved fuel processing efficiency, their costs are high due to the use of Pd metal and issues such as hydrogen embrittlement and sulfur tolerance need to be addressed. The PdAg₂₃ membranes used in previous experiments were tubes with a wall thickness of 178 μm. This is far too much Pd to be cost effective in an energy application. Development of composite membranes comprised of a thin Pd or Pd alloy film on a hydrogen-porous support or less expensive alternatives to Pd is required. Some advances have recently been made in achieving thinner membranes. For example, a composite membrane with Pd thickness as small as 0.5 μm has been developed.⁸ These composite metal membranes have low Pd loadings and high H₂ fluxes (~29 sccm/cm²·atm at 365°C).

A Pd membrane reactor was used to produce pure H₂ and a CO₂ rich stream from carbon monoxide and water over commercially available catalysts.⁹ These preliminary results demonstrate the viability of high pressure PMR operation. As much as 87% of the injected CO was converted into H₂ over an Fe-Cr-Cu oxide catalyst at 343°C, a pressure of 240 psia, and a H₂O:CO ratio of 2.6. The PMR has great potential in energy applications since it operates at more efficient conditions than conventional reforming and shifting systems and it produces pure H₂ for use in power generation and CO₂ for carbon sequestration. However, in order for PMRs to become a viable technology for energy applications, sulfur tolerance must be improved, membrane thickness (and therefore cost) must come down, and membrane fluxes and lifetimes must be improved.

Sulfur is ubiquitous in coal and must be removed prior to discharge of coal combustion products to the environment. Whether or not sulfur is removed up front or at the tail end of the overall process, sulfur tolerant membranes and catalysts are desired for systems utilizing coal gas. The PdCu₄₂ alloy has been reported to be sulfur tolerant.¹⁰⁻¹¹ Our work focuses on creating thin film composite membranes using this material.

DISCUSSION OF CURRENT ACTIVITIES

MEMBRANE DESIGN

The Pd membrane literature was reviewed and two of the most promising configurations are being fabricated. A Pd-alloy/refractory/Pd-alloy composite foil membrane (developed at Los Alamos National Lab), and Pd alloy thin films on porous ceramic supports.^{8,12} The foil composites are prepared by ion cleaning a refractory metal (V, Nb or Ta) or alloy and sputter depositing Pd (or Pd alloy) onto it *in-situ*. This eliminates the oxide/contaminant layer between the Pd and the foil resulting in higher hydrogen permeability.

The other method of composite membrane fabrication involves wet chemical methods. Commercially available porous ceramic membranes are cleaned, the ends are glazed, the surface is activated, and then they are electroless plated with Pd and then Cu. The membrane is heated in-situ to moderate temperatures (350-550°C) to promote intermetallic diffusion of the two metals. Characterization of both types of membrane materials is ongoing with respect to permeability and thermal stability under the water-gas shift reaction conditions.

PMR DESIGN

A test module has been designed and is being fabricated to accommodate tubular composite membranes (Figure 2). The catalyst particles are packed within the hydrogen separating membrane and the shell collects the permeated hydrogen. The new PMR test bench (Figure 3), with all stainless steel components will be used to test various catalysts and membrane materials at high pressures (up to 15 atm) for hydrogen recovery during reforming reactions as well as the impact of sulfur on performance.

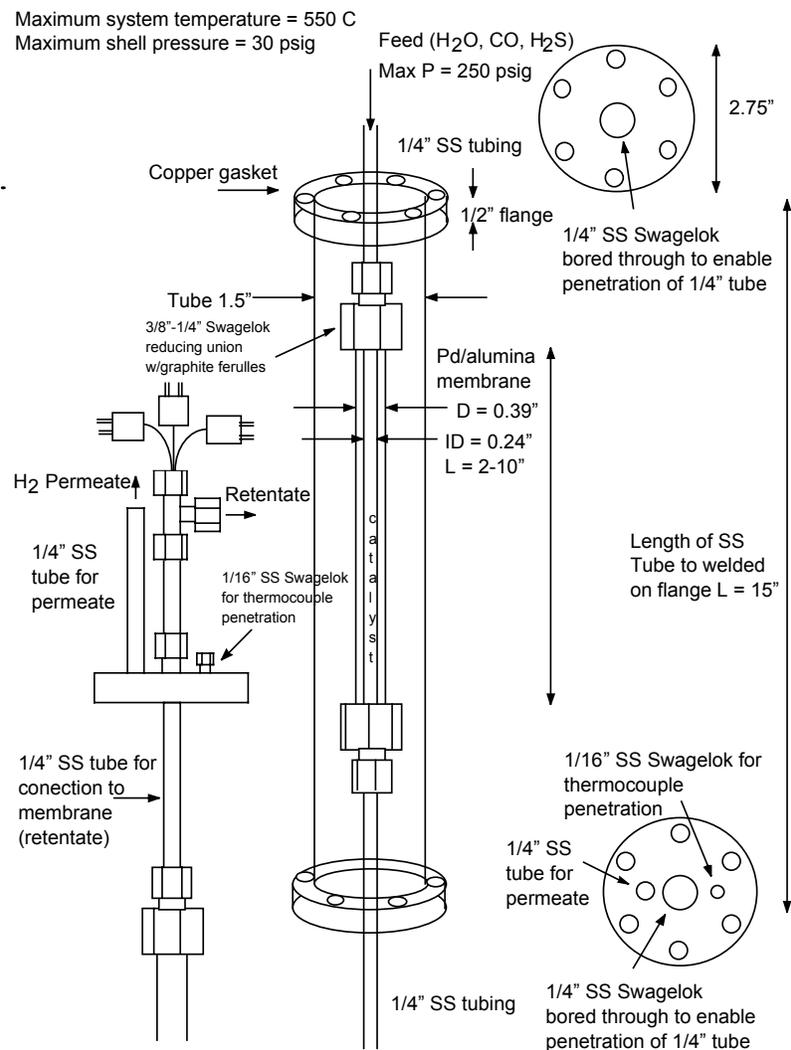


Figure 2. Schematic of composite membrane testing module.

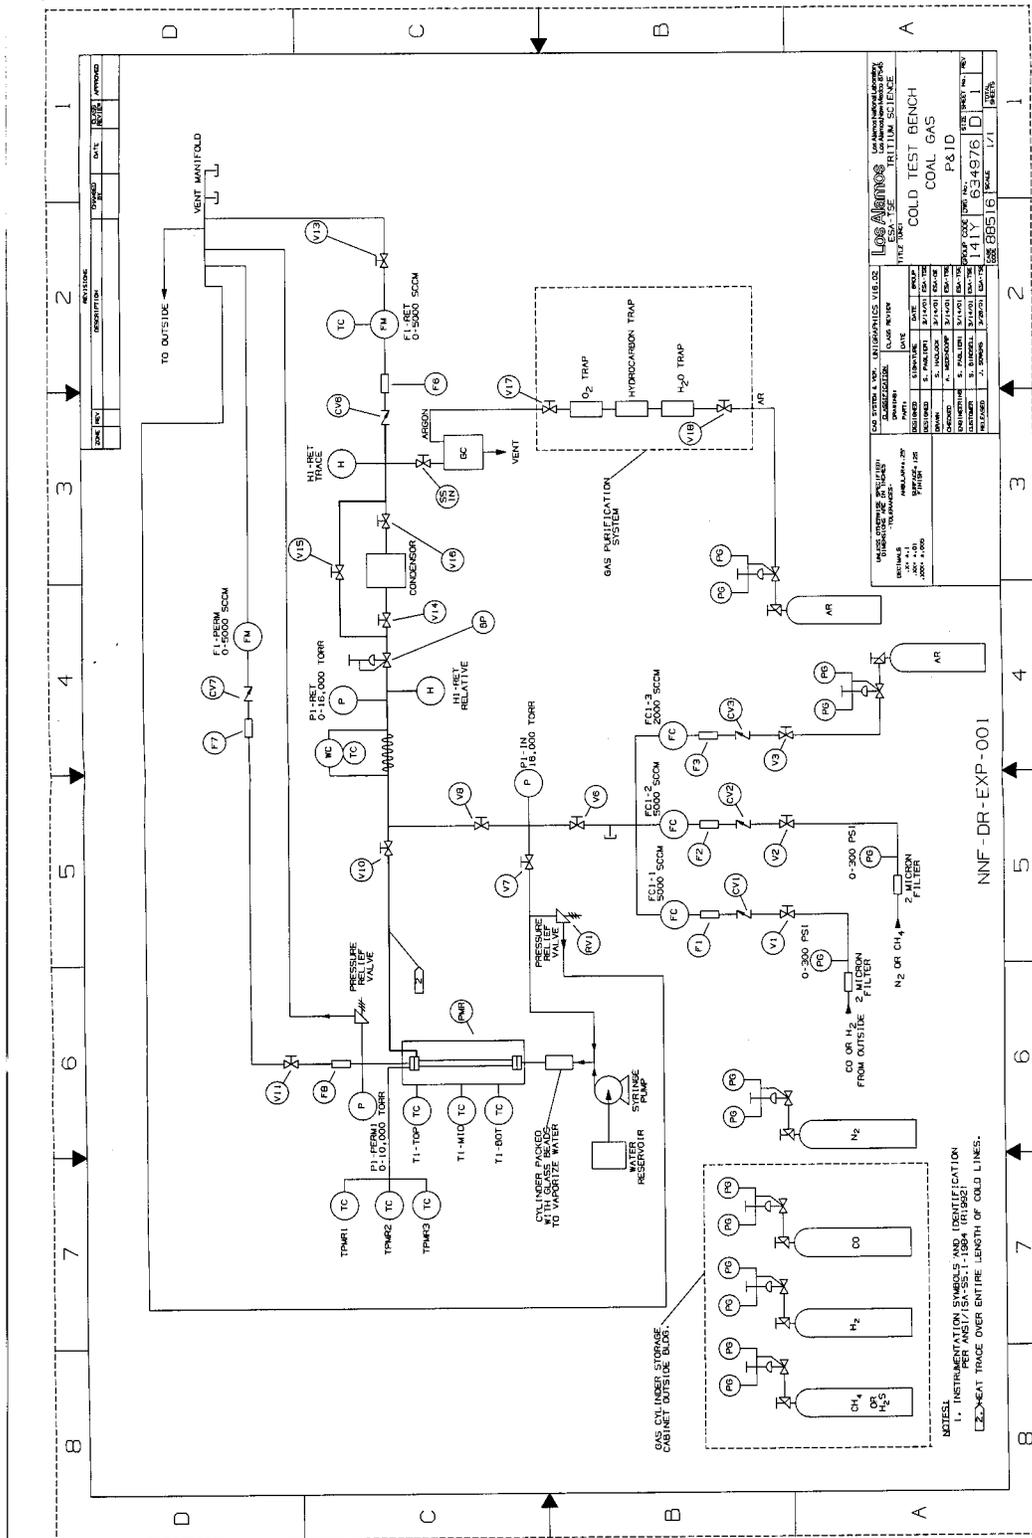


Figure 3. Test bench schematic.

CONCLUSIONS

The use of Pd alloy thin film composites will help lower the cost of hydrogen separation membranes while the use of alloys will reduce hydrogen embrittlement problems and may impart increased sulfur resistance. Fabrication and characterization of these materials for use as membrane reactors to test various catalysts is in progress.

ACKNOWLEDGEMENTS

This work was funded by the Advanced Materials Research Program, Office of Fossil Energy, U.S. Department of Energy. Thanks also to Don Gettemy, John Moya, Stan Bennett, Stephen Cole, Erica Larson, and Kevin Sessions for assistance.

REFERENCES

1. Birdsell, S. A. and Willms, R. S., 1995, "Modeling and Data Analysis of a Palladium Membrane Reactor for Tritiated Impurities Cleanup," *Fusion Tech.*, Vol. 28, No. 3, Part 1, pp. 530-537.
2. Willms, R. S. and Birdsell, S. A., 1995, "Palladium Membrane Reactor Development At The Tritium Systems Test Assembly," *Fusion Tech.*, 28, No. 3, Part 1, pp. 772-777.
3. Birdsell, S. A. and Willms, R. S., 1997 "Ultra-High Tritium Decontamination of Simulated Fusion Fuel Exhaust using a 2-Stage Palladium Membrane Reactor," Proceedings of the 12th Topical Meeting on Fusion Technology, Reno, NV, June 16-20, 1996, Vol. 30, No. 3, Part 2A, 905-910.
4. Birdsell, S. A. and Willms, R. S., 1997, "Tritium Recovery From Tritiated Water With a Two-Stage Palladium Membrane Reactor," *Fusion Eng. Des.*, Vol. 29-40, pp. 1041-4048, 1998.
5. Birdsell, S. A., Willms, R. S. and Dye, R. C., 1997, "Pure Hydrogen Production from Octane, Ethanol, Methanol, and Methane Reforming using a Palladium Membrane Reactor," Proceedings of the Thirty Second Intersociety Energy Conversion Engineering Conference, Honolulu, Hawaii, July 27-August 1, 1997, pp. 1942-6.
6. Birdsell, S. A., Willms, R. S., Arzu, P. and A. Costello, "Effect of Inlet Conditions on the Performance of a Palladium Membrane Reactor," Proceedings of the 17th IEEE/NPS Symposium on Fusion Engineering, San Diego, California, Oct. 6-10, 1997, pp. 301-303.
7. Birdsell, S. A. and Willms, R. S. "Pure Hydrogen Production From Gasoline Reforming Using A Palladium Membrane Reactor," Presentation Record of the 1998 Annual Meeting of the American Institute of Chemical Engineers, Nov. 15-20, Miami, FL.
8. Peachey, N., Snow, R. C., and Dye, R. C., 1996, "Composite Pd/Ta Metal Membranes for Hydrogen Separation", *J. Membrane Sci.*, Vol. 111, pp. 123-133.
9. Paglieri, S. N. and Birdsell, S. A. "Efficient production of pure hydrogen from simulated coal gas using a palladium membrane reactor," Proceedings of the 14th Annual Conference on Fossil Energy Materials, Knoxville, Tennessee, April 24-26, 2000, paper 1.5.
10. McKinley, D.L., 1967, "Metal alloy for hydrogen separation and purification," U.S. 3,350,845.
11. Edlund, D. A., 1996, "Membrane Reactor for H₂S Decomposition," in Advanced Coal-Fired Power Systems '96 Review Meeting, Morgantown, WV.
12. Paglieri, S. N., 1999, "Palladium and palladium--copper composite membranes for hydrogen separation," Ph.D. Thesis in Dept. of Chemical & Petrol. Eng., Colorado School of Mines, Golden, Colorado.